



THE UNIVERSITY *of* EDINBURGH

Edinburgh Research Explorer

## Tailoring dicobalt Pacman complexes of Schiff-base calixpyrroles towards dioxygen reduction catalysis

**Citation for published version:**

Askarizadeh, E, Yaghoob, SB, Boghaei, DM, Slawin, AMZ & Love, JB 2010, 'Tailoring dicobalt Pacman complexes of Schiff-base calixpyrroles towards dioxygen reduction catalysis', *Chemical Communications*, vol. 46, no. 5, pp. 710-712. <https://doi.org/10.1039/b923189g>

**Digital Object Identifier (DOI):**

[10.1039/b923189g](https://doi.org/10.1039/b923189g)

**Link:**

[Link to publication record in Edinburgh Research Explorer](#)

**Document Version:**

Peer reviewed version

**Published In:**

Chemical Communications

**Publisher Rights Statement:**

Copyright © 2009 by the Royal Society of Chemistry. All rights reserved.

**General rights**

Copyright for the publications made accessible via the Edinburgh Research Explorer is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

**Take down policy**

The University of Edinburgh has made every reasonable effort to ensure that Edinburgh Research Explorer content complies with UK legislation. If you believe that the public display of this file breaches copyright please contact [openaccess@ed.ac.uk](mailto:openaccess@ed.ac.uk) providing details, and we will remove access to the work immediately and investigate your claim.



Post-print of a peer-reviewed article published by the Royal Society of Chemistry.

Published article available at: <http://dx.doi.org/10.1039/B923189G>

Cite as:

Askarizadeh, E., Yaghoob, S. B., Boghaei, D. M., Slawin, A. M. Z., & Love, J. B. (2010). Tailoring dicobalt Pacman complexes of Schiff-base calixpyrroles towards dioxygen reduction catalysis. *Chemical Communications*, 46(5), 710-712.

Manuscript received: 05/11/2009; Accepted: 03/12/2009; Article published: 18/12/2009

## Tailoring dicobalt Pacman complexes of Schiff-base calixpyrroles towards dioxygen reduction catalysis\*\*

Elham Askarizadeh,<sup>1,2</sup> Sahar Bani Yaghoob,<sup>1,2</sup> Davar M. Boghaei,<sup>2</sup> Alexandra M. Z. Slawin<sup>3</sup>  
and Jason B. Love<sup>1,\*</sup>

<sup>[1]</sup>EaStCHEM, School of Chemistry, Joseph Black Building, University of Edinburgh, West Mains Road, Edinburgh, EH9 3JJ, UK.

<sup>[2]</sup>Department of Chemistry, Sharif University of Technology, P.O. Box 11155-3516, Tehran, Iran.

<sup>[3]</sup>EaStCHEM School of Chemistry, University of St. Andrews, North Haugh, St. Andrews, Fife, UK.


<sup>[\*]</sup>Corresponding author; e-mail: [jason.love@ed.ac.uk](mailto:jason.love@ed.ac.uk); fax: +44 (0)131 6504743;

<sup>[\*\*]</sup>We thank Prof. Eric McInnes of the University of Manchester and Dr. Paul Murray of the University of Edinburgh for help with EPR experiments, and the University of Edinburgh, the Sharif University of Technology, and the British Council for Iran for funding.

### Supporting information:

<sup>[†]</sup>Electronic Supplementary Information (ESI) available: full experimental, crystallographic and catalytic data and Figures S1 to S5. CCDC 749304 and 749305 See <http://dx.doi.org/10.1039/B923189G>

### Graphical abstract:

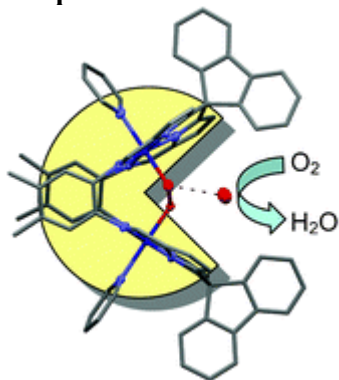

### Keywords:

porphyrin-corrole dyads; O bond activation; hangman porphyrins; fuel-cells; oxygen; reactivity; water, O-2; architectures; cobalt(III)

## Abstract


By modifying the mouth of a macrocyclic dicobalt Pacman complex, it is possible to both isolate new bridging-superoxo and hydroxyl complexes and to tune the reactivity of this system towards catalytic four-electron reduction of dioxygen to water.

## Introduction

The reduction of dioxygen is a chemical reaction intrinsic to fuel cells and aerobic organisms and relies on transition metal-based compounds or enzymes to manage the multiple proton and electron inventory during catalysis and ensure the efficient and selective generation of water. Much effort has gone into elucidating a fundamental understanding of this proton-coupled, multi-electron redox reaction,<sup>1</sup> in particular to help develop new, base-metal catalysts that are more robust and economical than the Pt-based materials currently used in polymer electrolyte membrane fuel cells.<sup>2</sup> In this context, molecular systems such as cofacial or Pacman dicobalt diporphyrins and corroles have proved very effective as catalysts for dioxygen reduction and the spectroscopic, structural, and theoretical analysis of these systems has provided much detail of the mechanism, in particular the identification of the superoxo complex  $[\text{Co}_2(\mu\text{-O}_2)(\text{diporph})]^+$  as a key director of selectivity.<sup>3-6</sup>

As an alternative to these porphyrinic complexes that are typically difficult and time-consuming to synthesise, we found that the dicobalt Pacman complex  $\text{Co}_2(\text{L})$ , in which the Schiff-base calixpyrrole ligand L has methyl *meso*-substituents, reacts with air to form a 90:10 mixture of the peroxo complex  $\text{Co}_2(\mu\text{-O}_2)(\text{py})_2(\text{L})$  and the superoxo cation  $\text{Co}_2(\mu\text{-O}_2)(\text{py})_2(\text{L})^+$ ; the former peroxo complex was characterised structurally and displayed a zigzag bonding mode of the  $\text{O}_2^{2-}$  unit between the two metals.<sup>7</sup> This mixture of compounds acted as a catalyst for the selective four-electron reduction of oxygen to water, albeit slowly and with decomposition, and we proposed that this poor activity profile was due to a combination of the formation of a stable hydroxyl-bridged cation  $\text{Co}_2(\mu\text{-OH})(\text{L})^+$  coupled with difficulty in accessing the superoxo cation, the entry point into the catalytic cycle.<sup>8</sup> We reasoned that the use of sterically-hindering, aryl *meso*-groups such as fluorenyl in  $\text{L}^{\text{F}}$  would both obviate the formation of  $\mu\text{-OH}$  bridged compounds and change subtly the electronic nature of these compounds, features that could promote better catalytic activity. We present here the significance of this ligand modification on the oxygen chemistry of its dicobalt complexes.

The  $\text{Co}^{\text{II}}\text{Co}^{\text{II}}$  complex  $\text{Co}_2(\text{L}^{\text{F}})$  was prepared as described previously,<sup>9</sup> and reacted with air in the presence of pyridine to form a mixture of two new complexes, the  $\text{Co}^{\text{III}}\text{Co}^{\text{III}}$  superoxo cation  $\{\text{Co}_2(\mu\text{-O}_2)(\text{py})_2(\text{L}^{\text{F}})\} \{\text{OH}\}$  and the mixed valence  $\text{Co}^{\text{II}}\text{Co}^{\text{III}}$  hydroxyl-bridged complex  $\text{Co}_2(\mu\text{-OH})(\text{py})(\text{L}^{\text{F}})$  that are related *formally* by  $\text{O}_2$  loss (Scheme 1).

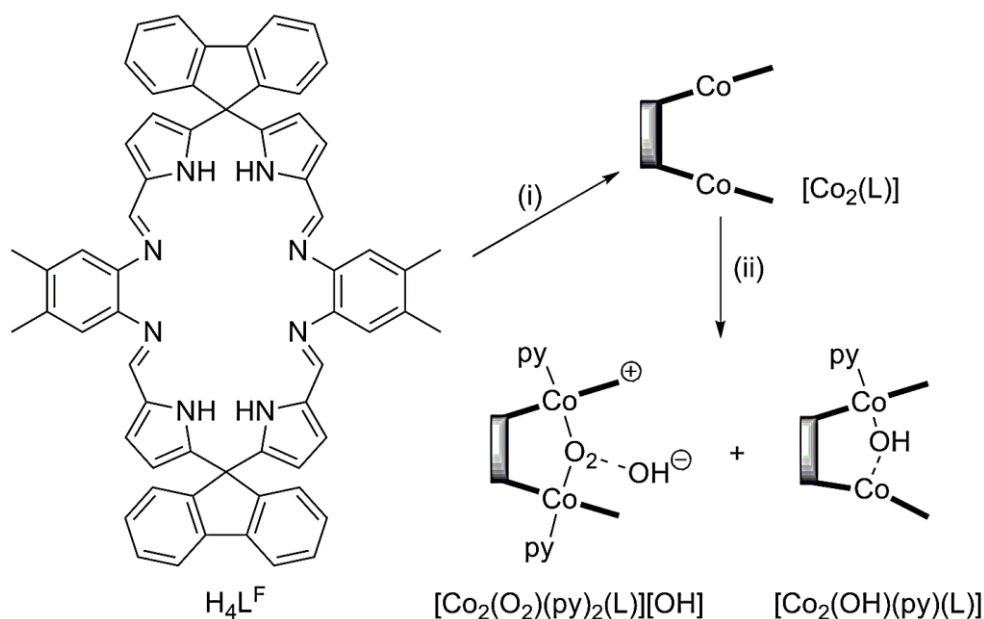


**Scheme 1.** Synthesis of dicobalt compounds of the macrocycle  $\text{H}_4\text{L}^{\text{F}}$ . Reagents and conditions: (i)  $2 [\text{Co}(\text{THF})\{\text{N}(\text{SiMe}_3)_2\}_2]$ , THF; (ii) Air, py, THF.

This reaction was monitored by  $^1\text{H}$  NMR and EPR spectroscopies.<sup>†</sup> In the  $^1\text{H}$  NMR spectrum (SI, Fig. S1), addition of pyridine to a  $\text{CDCl}_3$  solution of  $\text{Co}_2(\text{L}^{\text{F}})$  causes the well-resolved, but paramagnetically-shifted signals of  $\text{Co}_2(\text{L}^{\text{F}})$  to disappear and, on exposure of this mixture to air, new resonances to appear between +40 and -70 ppm that are consistent with the asymmetric environment of the new  $\text{Co}^{\text{II}}\text{Co}^{\text{III}}$  paramagnetic complex  $\text{Co}_2(\mu\text{-OH})(\text{py})(\text{L}^{\text{F}})$ . This formulation is supported further by addition of  $[\text{D}_5]$ -pyridine to the mixture which results in exchange of only one molecule of pyridine (SI, Fig. S1) and also by X-ray crystallography (see below). Significantly, there is no evidence of any diamagnetic peroxo complex  $\text{Co}_2(\mu\text{-O}_2)(\text{py})_2(\text{L}^{\text{F}})$  in any of these NMR spectra, which contrasts to that seen by us in the oxygenation reactions of  $\text{Co}_2(\text{L})$ .<sup>7</sup> In the X-band EPR spectrum in frozen  $\text{CHCl}_3$  (SI, Fig. S2), the broad, featureless resonance for  $\text{Co}_2(\text{L}^{\text{F}})$  at  $g$  2.214 is replaced by a less intense (24% by integration),  $S = \frac{1}{2}$  signal centred at  $g$  2.016 on exposure to air which is best assigned to the superoxo cation  $\text{Co}_2(\text{O}_2)(\text{L}^{\text{F}})^+$ ; no signal is seen in fluid solution. Simulation of this resonance in rhombic symmetry suggests that the oxygen radical is bound primarily to *one* Co centre, with  $g_x$  1.991,  $A_x$  11.5 G,  $g_y$  2.015,  $A_y$  14.0 G, and  $g_z$  2.068,  $A_z$  21.5 G, which contrasts to the 15-line EPR spectra seen normally for superoxo cobalt cofacial diporphyrin complexes and also for  $\text{Co}_2(\text{O}_2)(\text{L})^+$  in which the  $\text{O}_2^-$  is bound symmetrically between the two  $\text{Co}^{\text{III}}$  centres. This suggests that the  $\text{O}_2^-$  is bound either in an asymmetric manner within the cleft or that it coordinates to a single Co outside the cleft.

The superoxo complex  $\{\text{Co}_2(\mu\text{-O}_2)(\text{py})_2(\text{L}^{\text{F}})\} \{\text{OH}\}$  was isolated as an analytically-pure material from hot toluene solution.<sup>‡</sup> The frozen solution X-band EPR spectrum of this isolated material is identical to that seen in the *in-situ* experiments, and the IR spectrum displays a broad absorption at  $3398 \text{ cm}^{-1}$  which supports the

presence of hydrogen-bonded hydroxide; dark red prisms were grown from toluene from which the X-ray crystal structure was determined (Figure 1).†

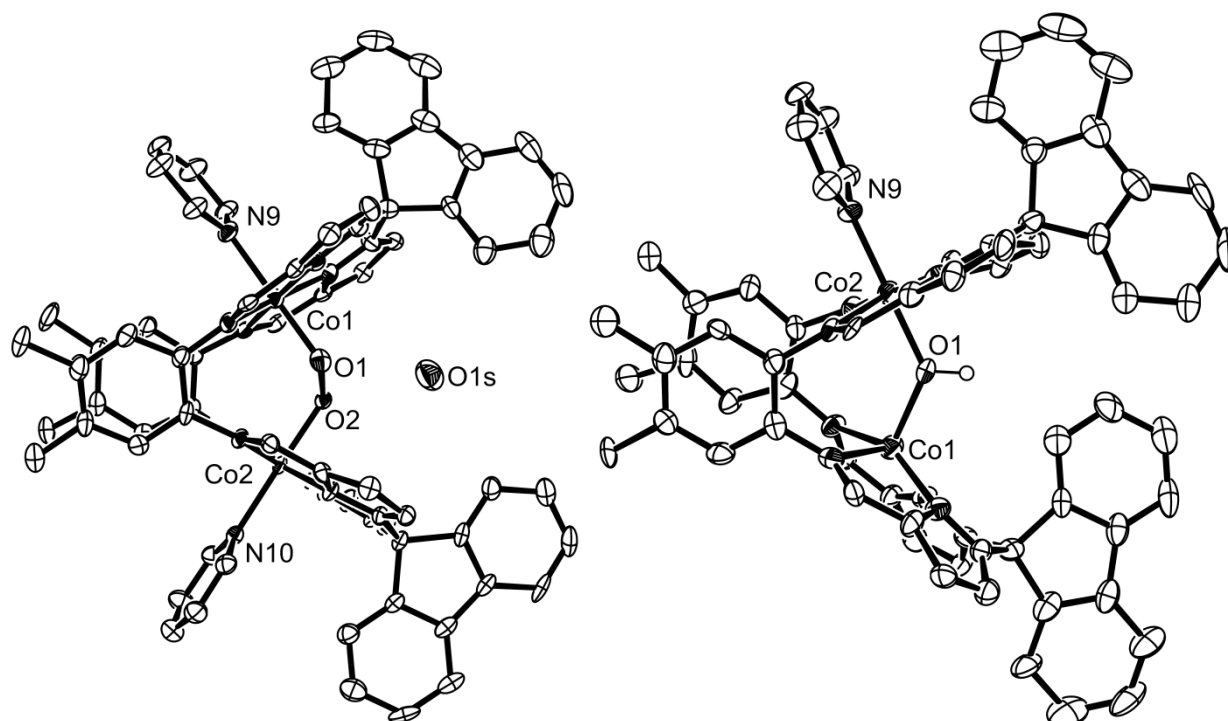

**Figure 1.** The solid state structures of  $\{\text{Co}_2(\mu\text{-O}_2)(\text{py})_2(\text{L}^{\text{F}})\}\{\text{OH}\}$  (left) and  $[\text{Co}_2(\mu\text{-OH})(\text{py})(\text{L}^{\text{F}})]$  (right). For clarity, all hydrogen atoms, except on the bridging hydroxyl oxygen and solvent of crystallisation have been omitted (displacement ellipsoids are drawn at 50 % probability).

In the solid state, the  $\text{O}_2$  is bound asymmetrically within the  $\text{Co}_2$  cleft ( $\text{Co1-O1}$  1.907(4),  $\text{Co2-O2}$  1.942(3) Å) with an  $\text{O1-O2}$  bond distance of 1.389(4) Å and a  $\text{Co1}\cdots\text{Co2}$  separation of 4.15 Å. Although the  $\text{O-O}$  distance is similar to that seen by us in the solid state structure of the *peroxo* complex  $\text{Co}_2(\mu\text{-O}_2)(\text{py})_2(\text{L})$  (1.361(3) Å), DFT calculations carried out by us on this latter peroxo compound and the singly-oxidised superoxo complex  $\text{Co}_2(\text{O}_2)(\text{py})_2(\text{L})^+$  showed the  $\text{O-O}$  bond distances to be identical (difference 0.001 Å) and so a poor measure of the electronic structure.<sup>8</sup> The slightly elongated  $\text{O-O}$  bond in this case is likely a consequence of the different ligand environment and the strong hydrogen-bonding interaction seen between  $\text{O1}$  and the hydroxide  $\text{O1s}$  ( $\text{O1}\cdots\text{O1s}$  2.801 Å). Analysis of a space-filling model of  $\{\text{Co}_2(\mu\text{-O}_2)(\text{py})_2(\text{L}^{\text{F}})\}\{\text{OH}\}$  (SI, Fig. S3) shows that  $\text{O1s}$  is nestled tightly in a cleft formed between the two fluorenyl substituents and the bridging  $\text{O}_2$  and that the fluorenyl substituents also display  $\pi$ -stacking interactions with a molecule of pyridine that binds in a cleft adjacent to the hydroxyl group. Intermolecular hydrogen-bonding interactions between metal-coordinated  $\text{O}_2$  and a donor such as  $\text{H}_2\text{O}$  or  $\text{ROH}$  are observed frequently in Ti, V and Mo  $\text{O}_2$  complexes in


which the O<sub>2</sub> is side-on bound (mean O<sub>2</sub>···O shortest contact 2.97 Å)<sup>10</sup> but to a much lesser extent in binuclear Co<sub>2</sub>(μ-O<sub>2</sub>) compounds (4 examples, range 3.187-3.653 Å; mean O<sub>2</sub>···O shortest contact 3.35 Å).<sup>11</sup> This interaction may suggest that the bound-O<sub>2</sub><sup>-</sup> in {Co<sub>2</sub>(μ-O<sub>2</sub>)(py)<sub>2</sub>(L<sup>F</sup>)}{OH} is more basic than in previous examples, a feature desirable in oxygen reduction catalysis in which protonation of the superoxo cation is a key mechanistic step that leads to O<sub>2</sub> scission and water production.<sup>5</sup> The <sup>1</sup>H NMR spectrum of analytically-pure, crystalline {Co<sub>2</sub>(μ-O<sub>2</sub>)(py)<sub>2</sub>(L<sup>F</sup>)}{OH} in CDCl<sub>3</sub> displays only resonances attributable to Co<sub>2</sub>(μ-OH)(py)(L<sup>F</sup>) and implies that the O<sub>2</sub> ligand is substituted readily by the OH<sup>-</sup> ligand.

The hydroxyl-bridged compound Co<sub>2</sub>(μ-OH)(py)(L<sup>F</sup>) is less soluble than the superoxo complex {Co<sub>2</sub>(μ-O<sub>2</sub>)(py)<sub>2</sub>(L<sup>F</sup>)}{OH}, and a few poorly-diffracting red prisms were isolated from CDCl<sub>3</sub> and the X-ray crystal structure determined (Figure 1).<sup>†</sup> As with the superoxo cation, a wedged, Pacman structure is seen, in this case with a hydroxyl-group bound asymmetrically between the two cobalt cations (Co1-O1 1.987(5), Co2-O1 1.916(5) Å) which are separated by 3.53 Å. The distorted octahedral coordination sphere of Co2 is completed by a molecule of pyridine, while Co1 adopts a square pyramidal geometry, moving 0.59 Å out of the N<sub>4</sub>-donor plane into the molecular cleft (*c.f.* -0.07 Å for Co2). Hydrogen-bonding contacts between the OH<sup>-</sup> group and both the fluorenyl group and a molecule of CHCl<sub>3</sub> are also seen (SI, Fig. S4) and may provide additional stability to the solid state structure. These geometric features, along with the longer Co-N(pyrrole) and Co-N(imine) bond distances seen for Co1 compared to Co2 and the absence of a counter ion, shows that Co<sub>2</sub>(μ-OH)(py)(L<sup>F</sup>) is a rare example of a mixed valence Co<sup>II</sup>Co<sup>III</sup> hydroxide in which the hydroxyl ligand bridges the two metals asymmetrically.

Preliminary evaluation of the catalytic activity of oxygenated Co<sub>2</sub>(L<sup>F</sup>) towards oxygen reduction was carried out using a modification of Fukuzumi and Guilard's method in which ferrocene derivatives (Fc) act as one-electron reductants in air-saturated PhCN in the presence of acid.<sup>12</sup> For Co<sub>2</sub>(L<sup>F</sup>), the best data were obtained using (C<sub>5</sub>H<sub>4</sub>Me)<sub>2</sub>Fe<sup>+</sup> with 9.6x10<sup>-5</sup> M of catalyst and 0.4 M of CF<sub>3</sub>CO<sub>2</sub>H (background production of ferrocenium was subtracted),<sup>4</sup> and resulted in the generation of (C<sub>5</sub>H<sub>4</sub>Me)<sub>2</sub>Fe<sup>+</sup> that became asymptotic at 6.2 mM concentration after 100 s (Fig. 2); this concentration of (C<sub>5</sub>H<sub>4</sub>Me)<sub>2</sub>Fe<sup>+</sup> equates primarily to a four-electron reduction process, *i.e.* the formation of H<sub>2</sub>O in preference to H<sub>2</sub>O<sub>2</sub> ([ (C<sub>5</sub>H<sub>4</sub>Me)<sub>2</sub>Fe<sup>+</sup> ] expected 6.8 x 10<sup>-3</sup> M with [O<sub>2</sub>] = 1.73 x 10<sup>-3</sup> M).<sup>†</sup>

Similar data were obtained using the less reducing Cp<sub>2</sub>Fe as the electron source although in this case asymptotic behaviour was only seen after 600 s (Fig 2, dashed lines). The use of lower concentrations of catalyst results in a decrease in total [Fc<sup>+</sup>], which may suggest that the catalytically-active species has a moderate turnover. Even so, the catalytic activity of Co<sub>2</sub>(L<sup>F</sup>) is enhanced significantly when compared to Co<sub>2</sub>(L) under the same conditions (Fig. 2, 0.024 mM, Cp<sub>2</sub>Fe<sup>+</sup>) and suggests that the ligand modification moving from L to L<sup>F</sup> has generated a much more robust catalyst. The rate of formation of (C<sub>5</sub>H<sub>4</sub>Me)<sub>2</sub>Fe<sup>+</sup> obeys pseudo-first order kinetics, and k<sub>obs</sub>, obtained from the pseudo-first order plot varies linearly with catalyst concentration with the second order rate constant k<sub>cat</sub> = 6.1 x 10<sup>2</sup> M<sup>-1</sup>s<sup>-1</sup> (SI, Fig. S5). This value of k<sub>cat</sub> is ca.

600 times less than that of the best cofacial diporphyrin catalyst for four electron O<sub>2</sub> reduction, Co<sub>2</sub>(DPX), where  $k_{\text{cat}} = 3.6 \times 10^5 \text{ M}^{-1}\text{s}^{-1}$  (DPX has a xanthene single pillar between the two porphyrins).<sup>12</sup>

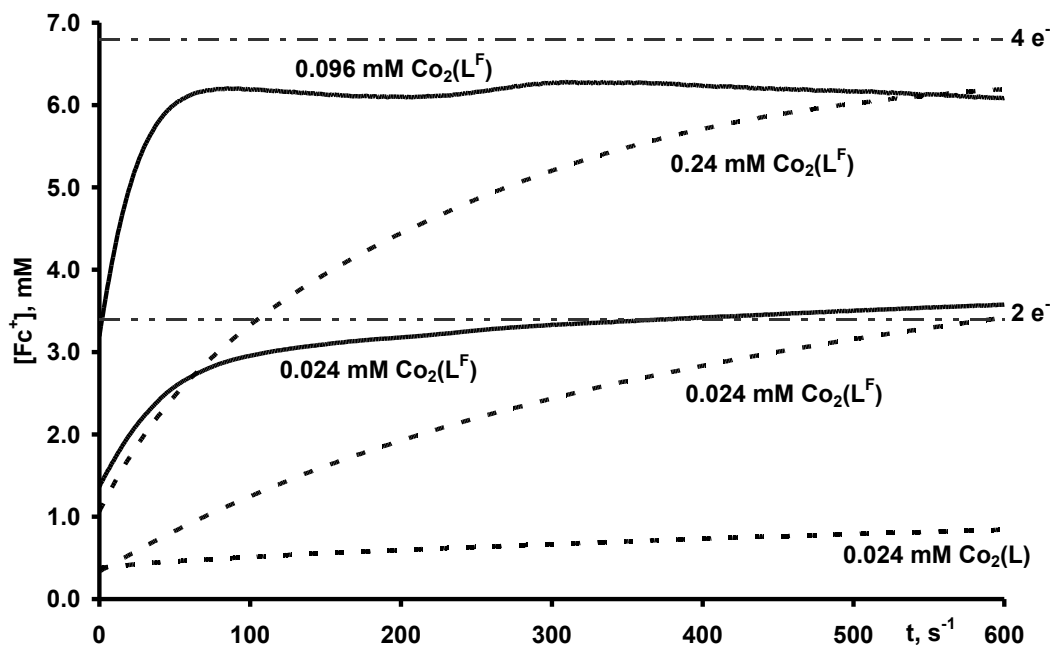

**Figure 2.** Time profiles for the formation of Fc<sup>+</sup> (solid lines (C<sub>5</sub>H<sub>4</sub>Me)<sub>2</sub>Fe<sup>+</sup>, dashed lines Cp<sub>2</sub>Fe<sup>+</sup>) monitored by UV-vis spectrophotometry in the electron transfer oxidation of Fc by O<sub>2</sub> (1.73 × 10<sup>-3</sup> M) catalysed by Co<sub>2</sub>(L<sup>F</sup>) or Co<sub>2</sub>(L) in the presence of 0.4 M CF<sub>3</sub>CO<sub>2</sub>H in PhCN at 298 K.

It is clear that the presence of the fluorenyl *meso*-substituents in Co<sub>2</sub>(L<sup>F</sup>) modifies significantly its reactions with O<sub>2</sub>, forming the two new compounds {Co<sub>2</sub>(μ-O<sub>2</sub>)(py)<sub>2</sub>(L<sup>F</sup>)}{OH} and Co<sub>2</sub>(OH)(py)(L<sup>F</sup>), and transforming a compound that is a relatively poor catalyst for four-electron dioxygen reduction into one that is considerably more effective. Detailed mechanistic assessments of the dioxygen chemistry of related cobalt cofacial diporphyrin complexes have shown that the entry point into the catalytic cycle for dioxygen reduction is the mixed valence cation Co<sub>2</sub>(diporph)<sup>+</sup> that reacts reversibly with O<sub>2</sub> to form the superoxo cation Co<sub>2</sub>(O<sub>2</sub>)(diporph)<sup>+</sup>; this latter compound is the key director for the reduction reaction.<sup>1, 4-6</sup> In contrast, the oxidation of Co<sub>2</sub>(L<sup>F</sup>) occurs spontaneously on exposure to air to form the mixed valence compound Co<sub>2</sub>(OH)(py)(L<sup>F</sup>) which can react with O<sub>2</sub> to form the key superoxo complex {Co<sub>2</sub>(μ-O<sub>2</sub>)(py)<sub>2</sub>(L<sup>F</sup>)}{OH}, so forming a mixture that are effective oxygen reduction catalysts.

## Notes and references

‡Syntheses:  $\{\text{Co}_2(\text{O}_2)(\text{py})_2(\text{L}^{\text{F}})\} \{\text{OH}\}$  – Solid  $\text{Co}_2(\text{L}^{\text{F}})$  (0.10 g) was dissolved in air-saturated THF (20 mL), causing an immediate red to dark brown colour change. Pyridine (0.04 mL) was added, and after 3 h, hexane (100 mL) which caused the products to precipitate. The precipitate was collected on a frit and extracted into hot toluene (60 °C, 60 mL), filtered, and reduced in volume. The crude product was precipitated by the addition of hexane and isolated as a brown powder (0.064 g, 54 %). Red brown crystals of  $\{\text{Co}_2(\text{O}_2)(\text{py})_2(\text{L}^{\text{F}})\} \{\text{OH}\} \cdot \text{py} \cdot 2\text{PhMe}$  were grown by hexane diffusion into a toluene/pyridine mixture.

Found: C, 70.47; H, 4.50; N, 11.46.  $\text{C}_{72}\text{H}_{55}\text{N}_{10}\text{O}_3\text{Co}_2$  requires: C, 70.53; H, 4.52; N, 11.42 %  $^1\text{H}$  NMR ( $\text{CDCl}_3$ , 360 MHz, 298 K):  $\delta_{\text{H}}$  36.7 (s, 1H), 32.5 (s, 2H), 31.3 (s, 2H), 30.5 (s, 2H), 21.6 (s, 6H), 20.6 (s, 2H), 17.5 (s, 1H), 16.8 (s, 2H), 14.5 (s, 1H), 14.4 (s, 1H), 13.7 (s, 1H), 11.9 (s, 1H), 10.0 (s, 1H), 5.5 (s, 1H), 4.8 (s, 1H), 4.4 (s, 2H), 2.1 (s, 1H), 0.9 (s, 1H), 0.8 (s, 2H), -5.0 (s, 1H), -5.8 (s, 1H), -16.4 (s, 6H), -22.3 (s, 1H), -30.4 (s, 1H), -63.1 (s, 2H); IR (KBr, nujol):  $\nu$  3398, 2927, 2853, 1559, 1463, 1377, 1054, 739, 446  $\text{cm}^{-1}$ ; UV-Vis (THF):  $\lambda_{\text{max}}$  332 nm ( $\ln \epsilon$  11.12), 257 (11.29), 221 (11.4); ESI-MS (+ve ion):  $m/z$  1052 ( $\text{M}^+ + \text{H} - \text{OH}$ , 100 %), 1036 ( $\text{M}^+ + \text{H} - \text{OH} - \text{O}$ , 52), 1019 ( $\text{M}^+ + \text{H} - \text{OH} - 2\text{O}$ , 12).

Red crystals of  $\text{Co}_2(\text{OH})(\text{py})(\text{L}^{\text{F}}) \cdot 4\text{CDCl}_3$  were grown by the slow evaporation of a sample of  $\{\text{Co}_2(\text{O}_2)(\text{py})_2(\text{L}^{\text{F}})\} \{\text{OH}\}$  in  $\text{CDCl}_3$ .

Crystal data  $\{\text{Co}_2(\mu\text{-O}_2)(\text{py})_2(\text{L}^{\text{F}})\} \{\text{OH}\}$   $\text{C}_{72}\text{H}_{55}\text{N}_{10}\text{O}_3\text{Co}_2(\text{C}_5\text{H}_5\text{N})(\text{C}_7\text{H}_8)_2$ ,  $M$  1489.49,  $a$  14.4714(4),  $b$  14.8327(4),  $c$  18.8570(6) Å,  $\alpha$  78.571(2),  $\beta$  75.865(2),  $\gamma$  71.571(2)°,  $T$  150(2) K, triclinic,  $P-1$ ,  $Z$  2, 43676 reflections 15079 independent,  $R(\text{int})$  0.084,  $R[F^2 > 2\sigma(F^2)]$  0.100, CCDC 749304;  $\text{Co}_2(\mu\text{-OH})(\text{py})(\text{L}^{\text{F}})$   $\text{C}_{67}\text{H}_{49}\text{N}_9\text{OCo}_2(\text{CHCl}_3)_4$ ,  $M$  1592.49,  $a$  20.627(2),  $b$  22.087(3),  $c$  30.628(4) Å,  $\alpha = \beta = \gamma = 90^\circ$ ,  $T$  150(2) K, orthorhombic,  $Pbca$ ,  $Z$  8, 85490 reflections 12745 independent,  $R(\text{int})$  0.29,  $R[F^2 > 2\sigma(F^2)]$  0.098, CCDC 749305.

[1] J.-M. Savéant, *Chem. Rev.*, 2008, **108**, 2348.

[2] B. Wang, *J. Power Sources*, 2005, **152**, 1; R. Bashyam and P. Zelenay, *Nature*, 2006, **443**, 63; P. H. Matter, E. J. Biddinger, and U. S. Ozkan, *Catalysis*, 2007, **20**, 338; N. Alonso-Vante and Y. Feng, *Phys. Stat. Sol. (B)*, 2008, **245**, 1792; M. Lefèvre, E. Proietti, F. Jaouen, and J.-P. Dodelet, *Science*, 2009, **324**, 71; J. P. Collman, A. Dey, Y. Yang, S. Ghosh, and R. A. Decréau, *Proc. Natl. Acad. Sci. U. S. A.*, 2009, **106**, 10528.

[3] S. Fukuzumi, *Chem. Lett.*, 2008, **37**, 808; P. D. Harvey, C. Stern, C. P. Gros, and R. Guillard, *Coord. Chem. Rev.*, 2007, **251**, 401; J. Rosenthal and D. G. Nocera, *Prog. Inorg. Chem.*, 2007, **55**, 483; J. P. Collman, P. S. Wagenknecht, and J. E. Hutchinson, *Angew. Chem. Int. Ed.*, 1994, **33**, 1537; K. M. Kadish,



J. Shen, L. Frémond, P. Chen, M. El Ojaimi, M. Chkounda, C. P. Gros, J.-M. Barbe, K. Ohkubo, S. Fukuzumi, and R. Guillard, *Inorg. Chem.*, 2008, **47**, 6726; K. M. Kadish, L. Frémond, F. Burdet, J.-M. Barbe, C. P. Gros, and R. Guillard, *J. Inorg. Biochem.*, 2006, **100**, 858; K. M. Kadish, L. Frémond, Z. Ou, J. Shao, C. Shi, F. C. Anson, F. Burdet, C. P. Gros, J.-M. Barbe, and R. Guillard, *J. Am. Chem. Soc.*, 2005, **127**, 5625; K. M. Kadish, J. Shao, Z. Ou, L. Frémond, R. Zhan, F. Burdet, J.-M. Barbe, C. P. Gros, and R. Guillard, *Inorg. Chem.*, 2005, **44**, 6744; J. Rosenthal, L. L. Chng, S. D. Fried, and D. G. Nocera, *Chem. Commun.*, 2007, 2642; J. D. Soper, S. V. Kryatov, E. V. Rybak-Akimova, and D. G. Nocera, *J. Am. Chem. Soc.*, 2007, **129**, 5069; S.-Y. Liu and D. G. Nocera, *J. Am. Chem. Soc.*, 2005, **127**, 5278; C. J. Chang, L. L. Chng, and D. G. Nocera, *J. Am. Chem. Soc.*, 2003, **125**, 1866; C.-Y. Yeh, C. J. Chang, and D. G. Nocera, *J. Am. Chem. Soc.*, 2001, **123**, 1513; K. M. Kadish, L. Frémond, J. Shen, P. Chen, K. Ohkubo, S. Fukuzumi, M. E. Ojaimi, C. P. Gros, J.-M. Barbe, and R. Guillard, *Inorg. Chem.*, 2009, **48**, 2571.

[4] J. Rosenthal and D. G. Nocera, *Acc. Chem. Res.*, 2007, **40**, 543.

[5] C. J. Chang, Z.-H. Loh, C. Shi, F. C. Anson, and D. G. Nocera, *J. Am. Chem. Soc.*, 2004, **126**, 10013.

[6] Y. Le Mest, C. Inisan, A. Laouenan, M. L'Her, J. Talarmin, M. El Khalifa, and J.-Y. Saillard, *J. Am. Chem. Soc.*, 1997, **119**, 6095.

[7] G. Givaja, M. Volpe, M. A. Edwards, A. J. Blake, C. Wilson, M. Schröder, and J. B. Love, *Angew. Chem. Int. Ed.*, 2007, **46**, 584; J. B. Love, *Chem. Commun.*, 2009, 3154

[8] M. Volpe, H. Hartnett, J. W. Leeland, K. Wills, M. Ogunshun, B. Duncombe, C. Wilson, A. J. Blake, J. McMaster, and J. B. Love, *Inorg. Chem.*, 2009, **48**, 5195.

[9]<sup>9</sup> E. Askarizadeh, A. M. J. Devoille, D. M. Boghaei, A. M. Z. Slawin, and J. B. Love, *Inorg. Chem.*, 2009, **48**, 7491.

[10] D. A. Fletcher, R. F. McMeeking, and D. Parkin, *J. Chem. Inf. Comput. Sci.*, 1996, **36**, 746.

[11] N. F. Curtis, W. T. Robinson, and D. C. Weatherburn, *Aust. J. Chem.*, 1992, **45**, 1663; D. D. Dexter, C. N. Sutherby, M. W. Grieb, and R. C. Beaumont, *Inorg. Chim. Acta*, 1984, **86**, 19; K. Hegetschweiler, O. Maas, A. Zimmer, R. J. Geue, A. M. Sargeson, J. Harmer, A. Schweiger, I. Buder, G. Schwitzgebel, V. Reiland, and W. Frank, *Eur. J. Inorg. Chem.*, 2003, 1340; S. Schmidt, F. W. Heinemann, and A. Grohmann, *Eur. J. Inorg. Chem.*, 2000, 1657.

[12] S. Fukuzumi, K. Okamoto, C. P. Gros, and R. Guillard, *J. Am. Chem. Soc.*, 2004, **126**, 10441.