



THE UNIVERSITY *of* EDINBURGH

Edinburgh Research Explorer

Opening the Gate

Citation for published version:

Fairen-Jimenez, D, Moggach, SA, Wharmby, MT, Wright, PA, Parsons, S & Düren, T 2011, 'Opening the Gate: Framework Flexibility in ZIF-8 Explored by Experiments and Simulations', *Journal of the American Chemical Society*, vol. 133, no. 23, pp. 8900-8902. <https://doi.org/10.1021/ja202154j>

Digital Object Identifier (DOI):

[10.1021/ja202154j](https://doi.org/10.1021/ja202154j)

Link:

[Link to publication record in Edinburgh Research Explorer](#)

Document Version:

Peer reviewed version

Published In:

Journal of the American Chemical Society

Publisher Rights Statement:

Copyright © 2011 by the American Chemical Society. All rights reserved.

General rights

Copyright for the publications made accessible via the Edinburgh Research Explorer is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

The University of Edinburgh has made every reasonable effort to ensure that Edinburgh Research Explorer content complies with UK legislation. If you believe that the public display of this file breaches copyright please contact openaccess@ed.ac.uk providing details, and we will remove access to the work immediately and investigate your claim.



This document is the Accepted Manuscript version of a Published Work that appeared in final form in *Journal of the American Chemical Society*, copyright © American Chemical Society after peer review and technical editing by the publisher. To access the final edited and published work see <http://dx.doi.org/10.1021/ja202154j>

Cite as:

Fairen-Jimenez, D., Moggach, S. A., Wharmby, M. T., Wright, P. A., Parsons, S., & Düren, T. (2011). Opening the Gate: Framework Flexibility in ZIF-8 Explored by Experiments and Simulations. *Journal of the American Chemical Society*, 133(23), 8900-8902.

Manuscript received: 09/03/2011; Accepted: 09/05/2011; Article published: 19/05/2011

Opening the Gate: Framework Flexibility in ZIF-8 Explored by Experiments and Simulations**

D. Fairen-Jimenez,^{1,*} S. A. Moggach,² M. T. Wharmby,¹ P. A. Wright,¹ S. Parsons² and T. Düren³

^[1]Institute for Materials and Processes, School of Engineering, The University of Edinburgh, UK.

^[2]EaStCHEM, School of Chemistry and Centre for Science at Extreme Conditions, The University of Edinburgh, UK.

^[3]School of Chemistry, University of St. Andrews, UK.


[*]Corresponding author; e-mail: David.Fairen@ed.ac.uk

[**]We thank Prof. N. A. Seaton and Prof. R. E. Morris for fruitful discussions, Prof. Chiu C. Tang for assistance at the I11 beamline at the Diamond Light Source (DLS), and DLS for beamtime. D. F-J. thanks the European Commission for a Marie Curie Intra-European fellowship (PIEF-GA-2009-236665). S. A. M. thanks the Royal Society of Edinburgh and the Scottish Government for a Personal Research fellowship.

Supporting information:

Experimental and simulation procedures, BET surface area representation and snapshots of N₂ adsorption on ZIF-8AP and ZIF-8HP. This material is available free of charge via the internet at <http://pubs.acs.org>

Graphical abstract:

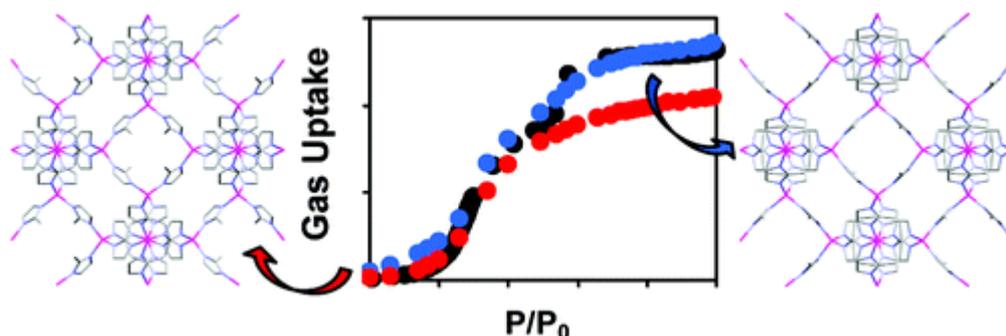

Abstract

ZIF-8 is a zeolitic imidazole-based metal-organic framework with large cavities interconnected by narrow windows. Because the small size of the windows, it allows in principle for molecular sieving of gases such as H₂ and CH₄. However, the unexpected adsorption of large molecules on ZIF-8 suggests the existence of structural flexibility. ZIF-8 flexibility is explored in this work combining different experimental techniques with molecular simulation. We show that the ZIF-8 structure is modified by gas adsorption uptake in the same way as it does at very high pressure (i.e. 14,700 bar) due to a swing effect in the imidazolate linkers, giving access to the porosity. Tuning the flexibility, and so the opening of the small windows, has further impact on the design of advanced molecular sieving membrane materials for gas separation, adjusting the access of fluids to the porous network.

Main text

Zeolitic imidazolate frameworks (ZIFs) have emerged as a very promising family of microporous metal-organic frameworks (MOFs).^{1,2} They combine the advantages of MOFs (i.e. high porosity and surface area, transition metal centers and tailored linkers) with high stability and framework diversity. Their adsorption properties can be tuned through chemical modification of the linker making them promising candidates for gas storage applications.^{3,4} Furthermore, many ZIFs exhibit large cavities interconnected by small windows which allows in principle for shape- and size- selective separations.

ZIF-8 is a prototypical structure with sodalite (SOD) topology that has been studied as a molecular sieve for the purification of hydrogen due to the narrow size of the 6-ring windows (~3.40 Å) that connect the large cavities (~11.6 Å of diameter).^{5,6} Because of the small window size, ZIF-8 is expected to separate hydrogen (2.89 Å kinetic diameter) from larger molecules including methane (3.80 Å) and nitrogen (3.60 Å). However, it has been observed experimentally that molecules which are theoretically too large to pass through the windows of the framework (i.e. in terms of the LJ collision diameter and the assumption that the framework is rigid), such as methane and nitrogen, are adsorbed in the material.^{1,7} In addition, predictions of the diffusivity of molecules in the rigid ZIF-8 structure⁸ show fundamental discrepancies to experimental data.^{5,6} The unexpected adsorption of large molecules and their relatively high diffusivity implies flexibility during the adsorption process. This flexibility in ZIF structures is fundamentally important since it modifies the diffusivity of gases through the porous network. A thorough understanding of this behavior is a pre-requisite to exploit this phenomenon in adsorption technology. In this work, we explore structural flexibility in ZIF-8 using different experimental techniques (gas adsorption, high pressure X-ray diffraction (XRD) and *in situ* synchrotron XRD), combined with grand canonical Monte Carlo simulations (GCMC).

Previous work demonstrated the effect of pressure up to 1.47 GPa or 14,700 bar on structural changes of ZIF-8.⁹ Though this pressure is far from a typical adsorption pressure (i.e. generally below 0.01 GPa or 100 bar), the structural changes observed in the diamond anvil cell experiments provide a first indication about the nature of the framework flexibility induced by adsorption at much lower pressures. At 1.47 GPa, a new phase was observed which we refer to as ZIF-8HP. This high-pressure phase maintained the I43m space-group symmetry of ZIF-8, but showed a reorientation of the imidazolate linkers, increasing the accessible pore volume and the size of the 6-ring windows. The structural change was found reversible after decreasing the pressure.

The experimental adsorption isotherm of N₂ at 77 K shows two steps occurring at 2×10^{-3} and 2×10^{-2} P/P₀ or 0.002 and 0.02 bar (Figure 1); the desorption process was completely reversible and no hysteresis was found. The fitting of the BET equation to both steps revealed the uptake of N₂ for the first and second step, corresponding to 36.9 and 49.4 molecules per unit cell, respectively (Supporting information, Table S1). This corresponds to an increase of 26 % in uptake going from the first to the second step. This two-step isotherm, which has also been observed in two other ZIFs with SOD topology (ZIF-90, ZIF-91),¹⁰ was previously interpreted as a result of a reorganization of the adsorbed nitrogen molecules during the adsorption process, rejecting the existence of structural changes.¹¹

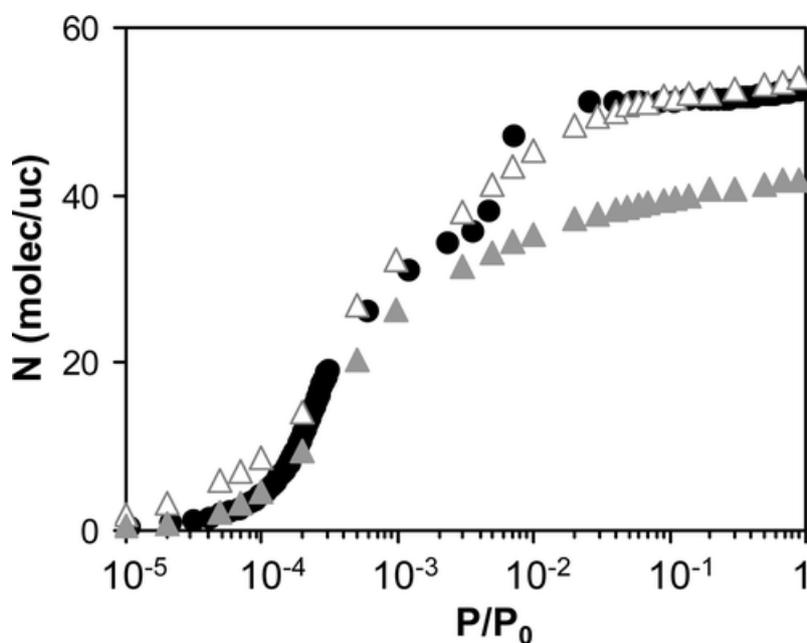


Figure 1. Semi-log plot of N₂ adsorption on ZIF-8 at 77 K: experimental, circles; and simulated data on ambient pressure structure, ZIF-8, closed triangles and high-pressure structure, ZIF-8HP, open triangles.

To investigate the step in the isotherm further and to relate it to possible changes in the structure of the ZIF-8, we conducted GCMC simulations of nitrogen at 77 K using both the ZIF-8HP structure and the structure of the conventional ZIF-8 (hereafter referred to as ZIF-8AP) following a similar approach as was used previously in, for example, the study of CO₂ adsorption in the flexible MOF MIL-53.¹² In contrast to the experimental curve, a standard Type I isotherm (i.e. without any step) was found in ZIF-8AP. The isotherm simulated in this structure fits the experimental isotherm in the low pressure range very well, correctly describing the Henry constant, which is a direct measure of the strength of the interactions. However, the prediction deviates from the experimental data when the pressure is higher than 2×10^{-4} P/P₀. In this case, the maximum uptake determined with the BET equation from the simulated isotherms corresponds to 35.8 molecules per unit cell, close to the first step of the experimental isotherm, but far below the second step. The differences between the experimental and the simulated isotherm at low and high pressures, together with the non-existence of steps in the simulation, indicate that the rigid model for ZIF-8AP is not able to describe fully the experimental behaviour.

When running the simulations on the ZIF-8HP phase previously observed at 1.47 GPa, the isotherm deviates from the experimental at low pressure, but predicts the step-shape of the experimental isotherm after 5×10^{-4} P/P₀ correctly. Here, the maximum uptake determined from the BET equation corresponds to 47.7 molecules per unit cell, similar to the experimental uptake after the step. This maximum uptake corresponds to a 33.4 % increase compared to the simulation on ZIF-8AP. The combination of both simulated adsorption isotherms on ZIF-8AP and ZIF-8HP before and after 2×10^{-4} P/P₀, respectively, is able to match the experimental isotherm indicating that ZIF-8 is undergoing the same structural changes on adsorption as observed in the diamond-anvil cell experiments under much higher pressures.

We further studied the structural change of ZIF-8 calculating geometrically the free pore volumes and accessible surface areas, and comparing them with those obtained from BET. Whereas the difference in the amount adsorbed before and after the step in the experimental isotherm (25.7 %) and in the simulated maximum adsorbed in two different structures (33.4 %), respectively, is substantial, no significant difference in either the free pore volumes or surface areas was observed (Table 1). This result seems counterintuitive at first, as an increase in the maximum uptake should be related to an increase in the pore volume. However, a detailed analysis of the molecular simulation results shows that the situation is more complicated. First, at 1.5×10^{-2} P/P₀, the N₂ molecules fill the same 36 positions of the nanocage as determined by Yildirim and co-workers from neutron powder diffraction experiments for the adsorption of CH₄ (Figure 2 and S2).¹³ A further pressure increase does not affect greatly the uptake. In the case of ZIF-8HP, N₂ molecules fill positions similar to the ones observed in ZIF-8AP before reaching the step in the adsorption isotherm. After the step, the subtle changes in the pore structure of ZIF-8HP compared to ZIF-8AP allow additional molecules to be accommodated leading to a more efficient packing through the rearrangement of previously adsorbed molecules and the insertion of new ones close to the 4- ring windows, a situation that does not arise in the case

of ZIF-8AP. Here, the linear shape of the N₂ molecules plays an important role in the packing during the adsorption process.

Table 1. Pore volume and surface areas for the different structures using GCMC

	Free Pore Volume [Å ³ /uc] ^[a]	Accessible Surface Area [Å ² /uc]	Accessible Surface Area [m ² /g] ^[b]	BET Surface Area [m ² /g]
ZIF-8AP	2918	606	1332	1279
ZIF-8HP	3034	598	1296	1706

[a] Obtained using a probe molecule with a diameter of 0 Å. [b] Obtained using a probe molecule with a diameter of 3.681 Å (i.e. N₂ molecule diameter used in the BET analysis).

In order to confirm that the ZIF-8HP structure is indeed observed at high nitrogen loadings, *in situ* powder XRD measurements at 77 K were conducted on station I11 at the Diamond light source on a fully evacuated sample of ZIF-8 and a separate sample which was loaded with N₂ at a relative pressure of 0.4 (i.e. after the step). Rietveld refinements were carried-out using TOPAS-A. Both the evacuated and N₂ loaded samples were refined from the ambient pressure coordinates from Moggach *et al.*⁹ in order to not bias the final model.

On comparing the N₂ containing ZIF-8 structure with ZIF-8HP, little difference is observed between the structures, with the N₂ loaded ZIF-8 (collected at several orders of magnitude lower in pressure) showing the same reorientation of the imidazolate linkers (Figure 3). This confirms the existence of a change in the structure caused by a swing effect of the imidazolate linker.

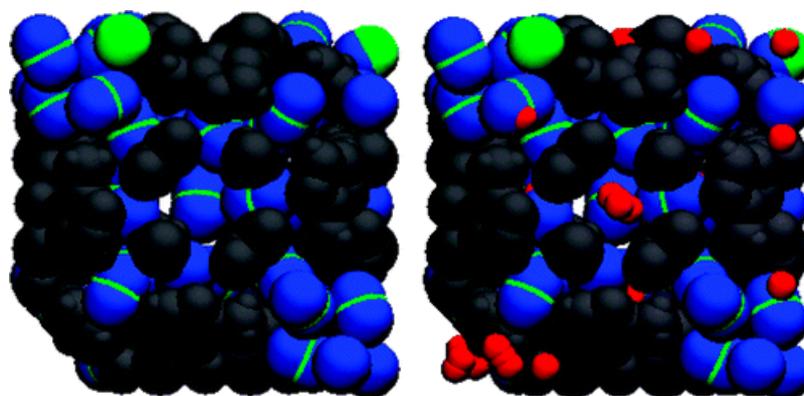


Figure 2. Snapshots of N₂, blue-green spheres, adsorption on ZIF-8HP, grey spheres, at 77 K (left) before and (right) after the step. Extra adsorbed N₂ molecules are represented by red spheres where their size has been scaled-down for an easier visualisation.

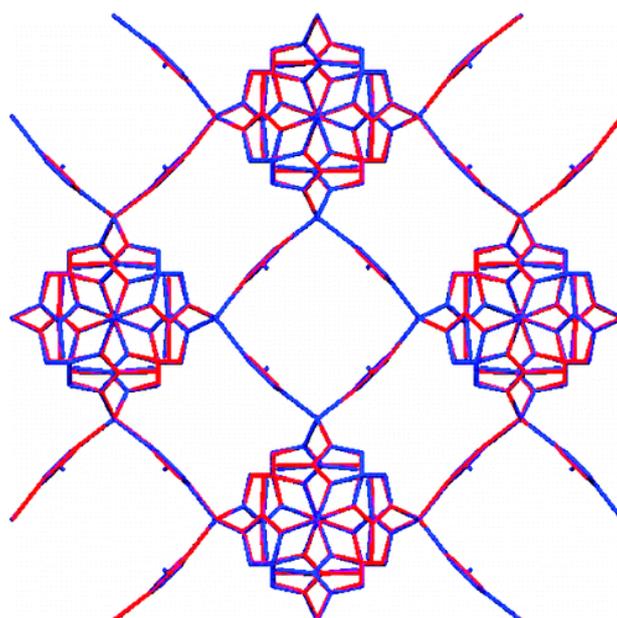


Figure 3. Overlay of ZIF-8 loaded with N₂ (blue) and ZIF-8HP (red).

In conclusion, we have shown that the ZIF-8 structure is modified by gas adsorption in the same way as at very high pressure in diamond anvil cell high-pressure experiments. Thus, the step in the nitrogen adsorption isotherm for ZIF-8 is caused by a structural change, which is also responsible for the non-expected adsorption of large molecules in ZIF-8 due to the enlargement of the windows size. In turn, the enlargement of the window size provokes faster diffusivity of molecules through the porous network.^{5,6} The addition of further molecules during the adsorption process close to the 4-ring windows is only possible due to a swing effect of the imidazolate rings. Compared to the high pressure experiments, the driving force that causes the change upon N₂ adsorption is the additional interaction the structure gets when adsorbing extra molecules. In turn, temperature, fluid-solid and fluid-fluid interactions play also an important role in the structural change and in the shape of the adsorption isotherm.¹⁴⁻¹⁶ Our results demonstrate that two conformations of ZIF-8 are needed to describe adsorption in this material: one derived from the crystal structure of the as-synthesized material, the other one obtained from high pressure XRD experiments. Thus, a correct description of the flexibility and structural changes of ZIF-8 is essential to precisely describe the adsorption performance over the whole range of pressure. Here, the diamond anvil cell experiments prove their usefulness for applications at much lower pressure since they are able to overcome any kinetic barrier between configurations in the same way as adsorbed fluid molecules do but are easier to carry out than in situ XRD experiments which require synchrotron radiation access.

The study of ZIF flexibility opens a new direction in the design of new porous solids. It has already been shown that ZIF-90 is suitable for post synthesis modification and keeps the SOD topology when other functional groups are introduced in the framework.^{2,10} The understanding of the role of the different building blocks and functional groups on the flexibility phenomena is of fundamental importance. Tuning this effect, and so the opening of the windows between cavities by changing the functional group in the imidazolate linker will directly affect the diffusivity of fluids through the porous network, which has fundamental impact on the performance of ZIFs as advanced molecular sieving membrane materials.

References

- [1] Huang, X. C.; Lin, Y. Y.; Zhang, J. P.; Chen, X. M. *Angew. Chem. Int. Ed.* **2006**, *45*, 1557-1559.
- [2] Banerjee, R.; Phan, A.; Wang, B.; Knobler, C.; Furukawa, H.; O'Keeffe, M.; Yaghi, O. M. *Science* **2008**, *319*, 939-943.
- [3] Kitagawa, S.; Kitaura, R.; Noro, S. *Angew. Chem. Int. Ed.* **2004**, *43*, 2334-2375.
- [4] Férey, G., *Chem. Soc. Rev.* **2008**, *37*, 191.
- [5] Bux, H.; Liang, F.; Li, Y.; Cravillon, J.; Wiebecke, M.; Caro, J. *J. Am. Chem. Soc.* **2009**, *131*, 16000-16001.
- [6] Bux, H.; Chmelik, C.; van Baten, J. M.; Krishna, R.; Caro, J. *Adv. Mater.* **2010**, *22*, 4741-4743.
- [7] Zhou, W.; Wu, H.; Hartman, M. R.; Yildirim, T. *J. Phys. Chem. C* **2007**, *111*, 16131-16137.
- [8] Haldoupis, E.; Nair, S.; Sholl, D. S. *J. Am. Chem. Soc.* *132*, 7528-7539.
- [9] Moggach, S.; Bennett, T.; Cheetham, A. *Angew. Chem. Int. Ed.* **2009**, *48*, 7087-7089.
- [10] Morris, W.; Doonan, C. J.; Furukawa, H.; Banerjee, R.; Yaghi, O. M. *J. Am. Chem. Soc.* **2008**, *130*, 12626-12627.
- [11] Park, K. S.; Ni, Z.; Côté, A. P.; Choi, J. Y.; Huang, R. D.; Uribe-Romo, F. J.; Chae, H. K.; O'Keeffe, M.; Yaghi, O. M., *Proc. Natl. Acad. Sci. U.S.A.* **2006**, *103*, 10186.
- [12] Ramsahye, N. A.; Maurin, G.; Bourrelly, S.; Llewellyn, P. L.; Loiseau, T.; Serre, C.; Férey, G. *Chem Comm.* **2007**, 3261-3263.
- [13] Wu, H.; Zhou, W.; Yildirim, T. *J. Phys. Chem. C* **2009**, *113*, 3029-3035.
- [14] Trung, T. K.; Trens, P.; Tanchoux, N.; Bourrelly, S.; Llewellyn, P. L.; Loera-Serna, S.; Serre, C.; Loiseau, T.; Fajula, F.; Férey, G. *J. Am. Chem. Soc.* **2008**, *130*, 16926-16932.
- [15] Llewellyn, P. L.; Horcajada, P.; Maurin, G.; Devic, T.; Rosenbach, N.; Bourrelly, S.; Serre, C.; Vincent, D.; Loera-Serna, S.; Filinchuk, Y.; Férey, G. *J. Am. Chem. Soc.* **2009**, *131*, 13002-13008.
- [16] Fairen-Jimenez, D.; Seaton, N. A.; Düren, T. *Langmuir* **2010**, *26*, 14694-14699.